

Study of gamma rays shielding parameters of some building materials used in Sudan

M.D.M. Ali¹, M.E.M. Eisa^{1,2*}, J.A. Mars^{3,4}, K.E.M. Mohamadain¹,
A.E. El faki¹, A. Hamed⁵, K.J. Cloete⁶, A.A. Beineen⁷

¹Physics Department, Sudan University of Science and Technology, Khartoum, Sudan

²Northern Border University, Department of Physics, Arar, Kingdom of Saudi Arabia

³Department of Medical Bioscience, University of the Western Cape, Private Bag X17, Bellville, of South Africa

⁴Faculty of Health & Wellness Sciences, Cape Peninsula University of Technology, Bellville, South Africa

⁵Department of Nuclear Engineering, Sudan University for Science and Technology, Khartoum, Sudan

⁶Department of Chemistry, University of the Western Cape, Private Bag X17, Bellville, South Africa

⁷Sudan Atomic Energy commission, Radiation Safety Institute, Khartoum, Sudan

ABSTRACT

► Original article

*Corresponding authors:

Mohamed Eisa, M.E., PhD.,

E-mail: memeisa@yahoo.com

Revised: April 2020

Accepted: June 2020

Int. J. Radiat. Res., January 2021;
19(1): 191-196

DOI: 10.18869/acadpub.ijrr.19.1.191

Background: This study investigated the γ -rays shielding properties of some building materials in Sudan has been investigated. **Materials and Methods:** Photons attenuation coefficients and half value layer (HVL) were experimented using Cs-137 and Co-60 sources. The measurements were performed to gauge the intensity of radiation when performed unshielded, the specific thickness of selected samples was examined, using an ion chamber placed at 2 meters from Cs-137 and Co-60. **Results:** The results indicated that the linear attenuation coefficient (μ) possesses a linear relationship with the corresponding densities of the samples studied and inversely with photon energy. HVL was directly proportional with photon energy. **Conclusion:** As a result of this evaluation the study concluded that selected samples were suitable as shielding material for gamma radiation in Sudanese laboratories.

Keywords: γ -radiation, attenuation coefficient, half value layer, shielding, building materials.

INTRODUCTION

Due to the use of radiation in many fields such as industrial, medical and agricultural, etc. So, the γ - radiation penetration through matter depends on the photon energy and the nature of absorbing material ⁽¹⁾. Ionizing radiation is considered a risk factor for cancer due to its potential to induce the stochastic effect, e.g., DNA damage, especially in rapidly cell-cycling tissues, such as the epithelial and endocrine tissues, in addition to immune and stem cells.

Gamma radiation can alter biologic molecules through direct or indirect mechanisms ⁽²⁾. With the increasing use of radioisotopes in many fields such as medical, industrial and agricultural. It becomes necessary to study the

different parameters related to the passage of gamma radiation through a material. Attenuation coefficient is an important parameter for study of interaction of radiation with matter that gives us the fraction of energy scattered or absorbed ⁽³⁾.

So that it is necessary to study different parameters related to the passage of γ -radiation through a building materials, and experimentally obtained the gamma ray shielding parameters such as half value layer, linear and mass attenuation coefficients to know the effectiveness of building materials as the gamma ray shielding.

Different workers have been calculated the attenuation coefficients in different categories such as in Lead and tungsten carbide cobalt (WC

-Co) Materials against γ - Irradiation, used Aluminum, Iron, Copper and Lead, in building block, concrete, iron and lead, ⁽⁴⁻⁷⁾ design and construction of light and heavy weight concrete biological shields from ionizing radiation, in heavy concrete, in Cement material ⁽⁸⁻¹⁰⁾, in clay, silica fume and cement samples, used clay-fly ash bricks, in boron doped clay for 662, 1173 and 1332 keV γ -rays ⁽¹¹⁻¹³⁾ in glass, concrete, marble, fly ash, cement and lime.

MATERIALS AND METHODS

Selected building materials (Clay, Cement mortar, Concrete Mix Design) as samples for shielding and prepared separately: the concrete mix was designed according to the British design method and the design result was as follows:

The mixture was designed to give strength of 25 N/mm² and the concrete was then mixed and casted into (150³ mm³ mm and 100³ mm³) cubes. For Cement mortar which mixed by cement was mixed with 4 sand and 0.5 water and cubes were casting in the same way for the concrete mix. For clay Proctor test was performed of clay sample to determine the optimum moisture content of the clay. The result was a 40% optimum moisture content, of clay weight.

The feature of lead and iron materials used was in form of slabs with different thicknesses, the density of lead, iron, concrete, cement and clay was 11.34 (g/cm³), 7.87 (g/cm³), 2.374 (g/cm³), 2.139(g/cm³) and 1.335 (g/cm³) respectively. The measurement was performed at secondary standard dosimetry laboratory (SSDL-Sudan) in order to determine the air kerma rate as radiation intensity at a reference distance from γ source (Co-60, Cs-137) located in OB-85 Irradiator two lead attenuators are available that are placed at the exit window of the irradiator, so shielding samples was placed at this point, and connected to Electrometer UNIDOS, Thermometer and barometer were used to conduct this measurement. Concerning dosimetry systems, the laboratory has one secondary standard ionization chamber

designed and manufactured at the Austrian research centre, Siebersdorf.

This chamber was calibrated at IAEA laboratory with its calibration traceable to the German National Laboratory (PTB)TM. Ionization chamber was placed at 2 meters from Cs-137 source as usual in reference standard measurements.

Measurements of linear attenuation coefficients; γ -ray beam used here was characterized in terms of air kerma as radiation intensity without attenuator further adding attenuator with constant operation voltage 400 volt, to calculate linear attenuation coefficient ⁽¹⁴⁾.

Linear attenuation coefficient

The Photon attenuation coefficient is an important parameter characterizing the penetration and diffusion of gamma rays in composite materials such as soil ⁽¹⁵⁾. Attenuation coefficient is one of the fundamental parameters that is important for characterization of the diffusion and penetration of gamma rays in a given medium ⁽¹⁶⁾.

The attenuation coefficient equation [1] measures the probability of all possible interactions between γ - rays and atomic nuclei, it is important for solving various problems in radiation physics and in radiation dosimetry. The probability of a photon interacting in a way with a given material, per unit path length is usually called the linear attenuation coefficient μ , is great importance in radiation shielding. Linear attenuation coefficients depend on the density ρ of the shielding material, the incident photon energy and the nature of the absorbing material.

$$\mu = \frac{1}{x} \ln\left(\frac{I_0}{I}\right) \quad (1)$$

Where μ is the linear attenuation coefficient in (cm⁻¹) and x is the thickness of the sample in (cm) ⁽¹⁷⁻¹⁹⁾.

Mass attenuation coefficient

Mass attenuation coefficient μ_m is an important parameter for study of interaction of

radiation with matter that gives us the fraction of energy scattered or absorbed, it is a measure of probability of interaction that occurs between incident photons and matter in a given mass per unit area thickness of the material encountered. It is a basic quantity used in the calculation of photon penetration and energy deposition in biological, shielding and other dosimetric materials. The magnitude of μ_m equation (2) ^(20,21) depends on the incident photon energy, the chemical structure and bonding in the absorbing material and parameters such as thickness and density ρ .

$$\mu_m = \mu / \rho \text{ cm}^2 \text{g}^{-1} \quad (2)$$

Half Value Layer (HVL)

The thickness of any given material where 50% of the incident energy has been attenuated is known as the half value layer HVL, useful parameters for understanding the interaction of γ -ray and depends on linear attenuation coefficient, is expressed in units of distance (cm). A half value of layer equation (3) ^(21,22, 23) of shielding material, $X_{1/2}$ defined at $I = \frac{I_0}{2}$, is given as:

$$X_{1/2} = \frac{0.693}{\mu} \quad (3)$$

RESULTS

Results illustrating the decrease of 662, 1173 and 1332 keV γ -rays with the increasing of the thickness of selected materials have been tested, for each energy the measurements were carried out ten times for all samples and the average values summarized in tables 1 to 4 which showed the value of doses through different lead and iron slabs thickness by using Cs-137 and Co-60 sources. The measuring time, temperature and pressure were 60s, 24.6 C and 968.9 hpa, respectively.

Also the attenuation coefficients and HVL for the all studied building materials have been obtained for 662, 1173 and 1332 keV γ -rays and the results have been listed in tables 5 and 6. Figures 1, 2, 3 and 4 show graphical patterns

linear attenuation coefficients (μ) values for the selected materials through two γ - rays sources, Cs-137 and Co-60, and the variation of linear attenuation coefficients with energy is shown as well. The linear attenuation coefficient of each one of the tested materials decreases with an increase in energy region (inverse relationship). This indicates photon attenuation in materials with increasing thickness analyzed at different energies of γ -rays. Figure 5 shows the comparison of HVL for the selected materials analyzed using two γ -rays sources, Cs-137 and Co-60. The results show a direct relationship between the HVL values and the energies. Figure 6 shows the comparison of density-dependence for the analyzed materials.

Table 1. The value of Doses through different lead and iron slabs thickness by using Cs-137 source. The measuring time, temperature and pressure were 60s, 24.6 and 968.9hpa, respectively.

| Lead thickness (cm) | Dose (μ GY) | Iron thickness (cm) | Dose (μ GY) | Frequency |
|---------------------|------------------|---------------------|------------------|-----------|
| 0.000 | 474.76 | 0.000 | 474.74 | 10 |
| 0.154 | 400.46 | 0.202 | 434.58 | 10 |
| 0.472 | 274.69 | 0.522 | 373.03 | 10 |
| 0.812 | 190.42 | 1.036 | 289.54 | 10 |
| 0.966 | 164.63 | 1.350 | 249.21 | 10 |

Table 3. The value of Doses through different building materials cubic's thickness by using Cs-137 source. The measuring time, temperature and pressure were 30s, 30 and 964.7hpa, respectively.

| Thickness (cm) | Dose (μ GY) through concrete shield | Dose (μ GY) through cement shield | Dose (μ GY) through clay shield | Frequency |
|----------------|------------------------------------------|----------------------------------------|--------------------------------------|-----------|
| 0 | 225.65 | 225.65 | 225.65 | 10 |
| 10 | 43.37 | 49.99 | 77.05 | 10 |
| 20 | 9.45 | 12.10 | 27.26 | 10 |
| 25 | 4.93 | 7.04 | 18.24 | 10 |
| 35 | 2.27 | 2.81 | 7.86 | 10 |

Table 4. The value of Doses through different building materials cubic's thickness by using Co-60 source. The measuring time, temperature and pressure were 30s, 34.5 and 964.8hpa, respectively.

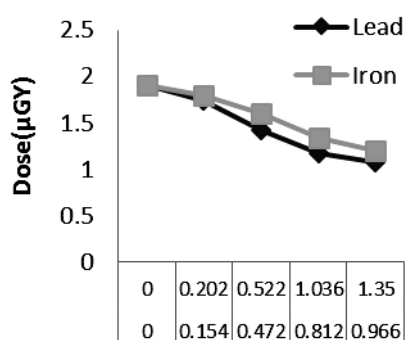
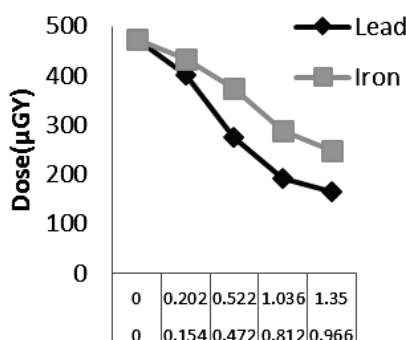
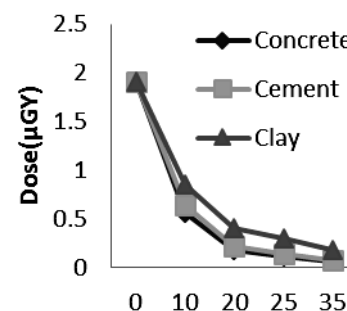
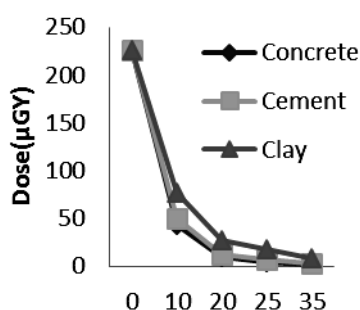
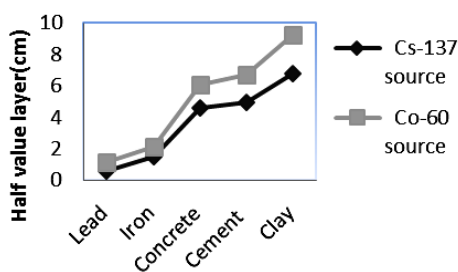
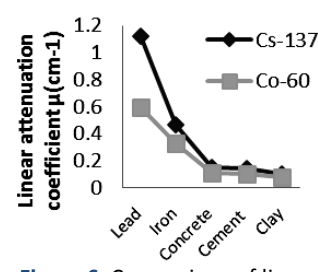
| Thickness (cm) | Dose (μ GY) through concrete shield | Dose (μ GY) through cement shield | Dose (μ GY) through clay shield | Frequency |
|----------------|------------------------------------------|----------------------------------------|--------------------------------------|-----------|
| 0 | 1.906 | 1.906 | 1.906 | 10 |
| 10 | 0.561 | 0.636 | 0.856 | 10 |
| 20 | 0.178 | 0.218 | 0.396 | 10 |
| 25 | 0.109 | 0.141 | 0.301 | 10 |
| 35 | 0.053 | 0.072 | 0.177 | 10 |

Table 5. Attenuation coefficient and half value layer for selected shielding materials using Cs-137 gamma rays.

| Materials | Linear attenuation coefficient $\mu(\text{cm}^{-1})$ | Standard error (cm^{-1}) | Mass attenuation coefficient $\mu_m(\text{cm}^2/\text{g})$ | Standard error (cm^2/g) | Half value layer(cm) | Standard error (cm) |
|-----------|------------------------------------------------------|-------------------------------------|------------------------------------------------------------|-------------------------------------------|----------------------|---------------------|
| Lead | 1.121 | 0.028 | 0.098 | 0.001 | 0.617 | 0.008 |
| Iron | 0.463 | 0.009 | 0.058 | 0.001 | 1.496 | 0.031 |
| Concrete | 0.151 | 0.007 | 0.063 | 0.003 | 4.593 | 0.236 |
| Cement | 0.139 | 0.006 | 0.065 | 0.003 | 4.965 | 0.206 |
| Clay | 0.101 | 0.003 | 0.076 | 0.002 | 6.779 | 0.175 |

Table 6. Attenuation coefficient and half value layer for selected shielding materials using Co-60 gamma rays.

| Materials | Linear attenuation coefficient $\mu(\text{cm}^{-1})$ | Standard error (cm^{-1}) | Mass attenuation coefficient $\mu_m(\text{cm}^2/\text{g})$ | Standard error (cm^2/g) | Half value layer(cm) | Standard error (cm) |
|-----------|------------------------------------------------------|-------------------------------------|------------------------------------------------------------|-------------------------------------------|----------------------|---------------------|
| Lead | 0.594 | 0.015 | 0.051 | 0.001 | 1.167 | 0.034 |
| Iron | 0.325 | 0.023 | 0.041 | 0.002 | 2.137 | 0.161 |
| Concrete | 0.114 | 0.009 | 0.046 | 0.004 | 6.084 | 0.484 |
| Cement | 0.104 | 0.007 | 0.048 | 0.004 | 6.691 | 0.497 |
| Clay | 0.075 | 0.006 | 0.056 | 0.005 | 9.267 | 0.699 |


Figure 1. Attenuation of Co-60 gamma rays as a function of thickness through different shield materials.

Figure 2. Attenuation of Cs-137 gamma rays as a function of thickness through different shield materials.

Figure 3. Attenuation of Co-60 gamma rays as a function of thickness through different shield materials.

Figure 4. Attenuation of Cs-137 gamma rays as a function of thickness through different shield materials.

Figure 5. Comparison of half value layer of different Materials using different γ -rays sources.

Figure 6. Comparison of linear attenuation coefficients of materials shield as a function of photon energy.

DISCUSSION

In the present study, radiological parameters such as the Co-60 and Cs-137 equivalent activity, the gamma index was determined to

assess the radiation hazards associated with the samples ⁽²⁶⁾. The representative level index, the indoor absorbed dose rate and the annual effective dose all the cement samples considered do not pose any significant source of radiation

hazard and the use of the cement samples in construction of dwellings is considered to be safe for inhabitants ⁽²⁷⁾. Building materials have been evaluated and discussed in terms of attenuation coefficients and HVL for different γ - rays energies. Energy absorption, in particular have been well used. Thus, many investigations subsequent to Goldstein and Wilkins have produced these kinds of buildup factors ^(24, 25). The variations in activity concentration among the building materials may be attributed to their radioactive mineral content and the geological, geochemical and geographical origins of the raw materials, among other factors ⁽²⁸⁾. The investigated materials are commonly used as building materials in Sudan, results displaying the linear attenuation coefficients decrease with the increasing of photon energy as well as HVL increase with photon energy increasing for the tested materials. From the present study, it was the increasing of photon energy as well as HVL increase with photon energy increasing for the tested materials. From the present study, it was found that among the investigated building materials they can be used as a gamma ray shielding materials in educational university. These important observations clearly demonstrate the identification of γ -rays by measuring the pulse height distribution in different and mixed materials radiation field. Due to lower intensities of radiation sources, the material samples are all too thin to test shielding effects perfectly in deep penetration situations in our experiments, however the annual effective dose due to direct exposure of operating personnel is ranged from 0.003 to 0.14 mSv. The annual effective dose of operating personnel due to dust inhalation ranged from 0.003 to 0.16 mSv, it is suggested here that it is advisable to monitor the radioactivity levels of materials from a new source before using it as a building material ^(29, 30). Such a large disparities in the concentrations of the radionuclides in building block samples within be explained with the variation in the radionuclide concentrations of the sand component of the blocks ⁽³¹⁾. This fact is important from the point of view of selecting

suitable materials for use in building and construction especially concerning those which have large variations in their activities, ⁽³²⁾. That shows some high-density materials can stop radiation; however, pure materials cannot form a stable substance such as cement or clay except in extreme situations. Therefore, the combination of different materials is required ⁽³³⁾. Building materials should be exempted from all restrictions concerning their radioactivity, if the excessive gamma radiation due to those materials causes the increase of the annual effective dose received by an individual by a maximum value of 0.3 mSv ⁽³⁴⁾.

CONCLUSION

Therefore, it may be possible to carry out the design of a shield in a purely analytical manner with the condition that the cross section of the absorption and attenuation coefficients are available for all interactions at all energies. The results of this study are challenges for the government and encourage it to disseminate radioprotection culture among the people who is concerned with radiation. The heat and radiation resistance of materials should be studied quantitatively in experiments among all radiation areas and these results will help as a data base for future. With this information on hand, future investigations will allow us to enhance controlling the radiation.

ACKNOWLEDGMENT

The authors would like to thank Sudan University of Science & Technology, Sudan Atomic Energy commission, Radiation Safety Institute, University of Khartoum, Construction and Roads Research Institute, for their help and support all through the work.

Conflicts of interest: Declared none.

REFERENCES

- Bouzarjomehri F, Baya T, Dashti M H, Ghisari J, Abdoli N (2006) ^{60}Co γ - ray attenuation coefficient of barite concrete. *Iran J Radiat Res*, **2(4)**: 71-75.
- Merola Y de L, Cunha Ta. Neves da, Schenka AA, Silva NC (2017) Natural environmental gamma radiation exposure and prevalence of breast cancer in Poços de Caldas, MG, Brazil. *Int J Radiat Res*, **15(4)**: 413-418.
- Al-khawlanly Abdu Hamoud, Khan AR, Pathan JM (2019) Investigation of radiation shielding properties for some soil samples for use in shields against gamma-rays from different nuclides. *Bulletin of pure and applied sciences*, **38(1)**: 32-45.
- Buyuk B and Tugrul A (2014) Comparison of lead and WC-Co materials against gamma irradiation. *Acta Physica Polonica a*, **125**: 423-425.
- Reda SM (2016) Gamma ray shielding by a new combination of aluminum, iron, copper and lead using MCNP5. *Arab Journal of Nuclear Science and Applications*, **94(4)**: 211-217.
- Adedoyin O and Ayodeji A (2016) Measurement of shielding effectiveness of building blocks against 662 KeV photons. *Journal of Physical Science*, **27(2)**: 55-65.
- Samarin A (2013) Use of concrete as a biological shield from ionising radiation. *Energy and Environmental Engineering*, **1(2)**: 90-97.
- Aghamiri SMR, Mortazavi S MJ, M.A. Shirazi M, Baradaran Ghahfarokhi M, Rahmani F, Amiri A, Jarideh S (2014) Production of a novel high strength heavy concrete using tourmaline and galena for neutron and photon radiation shielding. *Int J Radiat Res*, **12(3)**: 277-282.
- Guan H, Liu S, Duan Y, Cheng J I (2006) Cement based electromagnetic shielding and absorbing building materials. *Cement & Concrete Composites*, **28**: 468-474.
- Akbulut S, Sehhatigdiri A, Eroglu H, Çelik S (2015) A research on the radiation shielding effects of clay, silica fume and cement samples. *Radiation Physics and Chemistry*, **117**: 88-92.
- Singh H, Brar GS, Singh MK, Mudahar G (2015) Experimental investigation of clay-flyash bricks for gamma ray shielding. *Nuclear Engineering and Technology*, **48(5)**: 1230-1236.
- Akkurt IH and Canakci H (2011) Radiation attenuation of boron doped clay for 662, 1173 and 1332 keV gamma rays. *Int J Radiat Res*, **9(1)**: 37-40.
- Charanjeet S, Tejbir S, Ashok K, Gurmeh S M (2004) Energy and chemical composition dependence of mass attenuation coefficients of building materials. *Annals of Nuclear Energy*, **31**: 1199-1205.
- IAEA (2000) Calibration of radiation protection monitoring instruments. Safety report series. IAEA Safety Standards Series.
- M Chaudhari Laxman and V Raje Dayanand (2012) study of photon attenuation coefficient of soil samples at gamma ray energy from 122 keV to 1330 keV. *Research Journal of Chemical Sciences*, **2(2)**: 49-53.
- Annual Report (2017). 104th Indian Science Congress Association, S.V. University, Ordinal 104th Affiliation, Department of Science and Technology, Ministry of Science and Technology, Government of India. Kolkata.
- Alam MN, Miah MMH, Chowdhury MI, Kamal M, Rahman R (2001) Attenuation coefficients of soils and some building materials of Bangladesh in the energy range 276 - 1332 keV. *Applied Radiation and Isotopes*, **54**: 973-976.
- El-Sayed Abdo A (2002) Calculation of the cross-sections for fast neutrons and gamma-rays in concrete shields. *Annals of Nuclear Energy*, **29**: 1977-1988.
- Salinas ICP, Contib CC, Lopesb RT (2006) Effective density and mass attenuation coefficient for building material in Brazil. *Applied Radiation and Isotopes*, **64**: 13-18.
- Elmahroug Y, Tellili B, Souga C (2015) Determination of total mass attenuation coefficients, effective atomic numbers and electron densities for different shielding materials. *Annals of Nuclear Energy*, **75**: 268-274.
- El-Sayed AWA, Michael AF, Bourham MA (2016) Gamma-ray mass attenuation coefficient and half value layer factor of some oxide glass shielding materials. *Annals of Nuclear Energy*, **96**: 26-30.
- Ravinder S, Sukhpal S, Gurmeh S, Singh Kulwant S T (2017) Gamma Radiation Shielding Properties of Steel and Iron Slags. *New Journal of Glass and Ceramics*, **7**: 1-11.
- Akkurt I, Başyigit B, Akkaş A, Kılınçarslan Ş, Mavia B, Günoğlu K (2012) Determination of some heavyweight aggregate half value layer thickness used for radiation shielding. Proceedings of the International Congress on Advances in Applied Physics and Materials Science, Antalya, 121. Turkey.
- Hu H, Wang Q, Qin J, Wu Y, Zhang T, Xie, Xinbiao Z, Jiang X, Zhang G, Hu Xu H, Zheng X, Zhang J, Liu W, Li Z, Zhang B, Li L, Song Z, Ouyang X, Zhu J, Zhao Y, Mi, XDong Z, Li C, Zhenyu Jiang Z, Zhan Y (2008) Study on composite material for shielding mixed neutron and -rays. *IEEE Transactions on Nuclear Science*, **55(4)**: 2376-2384.
- Tanaka S, Harima Y, Hirayama H, Ban S, Nakamura T, Kosako T, Uwamin Y, Hashikura H, Kanai Y, Kawal M, Yukio Sakamoto Y, (1988). Annotated bibliography and discussion of gamma-ray buildup factors. *Int J Radiat*, **39(3)**: 241-252.
- Seref T (2009) Radiological impacts of the usability of clay and kaolin as raw material in manufacturing of structural building materials in Turkey. *J Radiol Prot*, **29**: 75-83.
- Şeref T and Gürbüz G (2007) Radiological significance of cement used in building construction in Turkey. *Radiation Protection Dosimetry*, **129(4)**: 391-6.
- Khandoker A, Farhana M, Mayeen U K, Mohideen S F, Aeman E, Yusoff M, Sailesh S, Hasan A (2015) Assessment of natural radioactivity levels and potential radiological risks of common building materials used in bangladeshi dwellings. *PLoS one*, **10(10)**: e0140667.
- Şeref T and Gürbüz G (2008) Radiological significance of cement used in building construction in Turkey. *Radiation Protection Dosimetry*, **129(4)**: 391-6.
- Jamal A, Wael S, Muhammad B, Feras A (2006) Exposure to radiation from the natural radioactivity in Jordanian building materials. *Radiation Protection Dosimetry*, **118(1)**: 93-96.
- Farai IP and Ademola JA (2005) Radium equivalent activity concentrations in concrete building blocks in eight cities in Southwestern Nigeria. *J Environ Radioact*, **79(2)**: 119-25.
- Nour KA (2005) Measurement of natural radioactivity in building materials in Qena city. *Upper Egypt Journal of Environmental Radioactivity*, **83**: 91-99.
- Mohammad A (2019) Gamma radiation shielding properties of glasses within the TeO₂-TiO₂-ZnO system. *Radiation Acta*, **107(6)**: 1-6.
- Asgharizadeh F, Abbasi A, Hochaghani O, Gooya ES (2012) Natural radioactivity in granite stones used as building materials in Iran. *Radiat Prot Dosimetry*, **149(3)**: 321-326.