

## Natural radioactivity levels and evaluation of radiological hazards in Usakos marble, Erongo region, Namibia

S.A. Onjefu<sup>1\*</sup>, N.N. Johannes<sup>1</sup>, J. Abah<sup>2</sup>, L.A. Onjefu<sup>3</sup>, S. Mwiya<sup>4</sup>

<sup>1</sup>Department of Natural and Applied Sciences, Faculty of Health and Applied Sciences, Namibia University of Science and Technology, Windhoek, Namibia

<sup>2</sup>Department of Mathematics, Science and Sport Education, Faculty of Education, University of Namibia, Katima Mulilo Campus, Namibia

<sup>3</sup>Department of Civil and Environmental Engineering, Faculty of Engineering, Namibia University of Science and Technology, Windhoek, Namibia.

<sup>4</sup>Foresight Group Namibia, P.O. Box 1839, Windhoek, Namibia

### ABSTRACT

#### ► Original article

**\*Corresponding author:**  
Onjefu Sylvanus Ameh, Ph.D.,  
E-mail: [sonjefu@nust.na](mailto:sonjefu@nust.na)

**Received:** November 2020

**Final revised:** September 2021

**Accepted:** October 2021

*Int. J. Radiat. Res., April 2022;*  
20(2): 403-409

DOI: 10.52547/ijrr.20.2.22

**Keywords:** Natural radioactivity, radiological hazards, marble, Usakos, Erongo.

**Background:** Most parts of the Erongo region of Namibia have shown high background radiation. The aim and objective of this study is to determine the natural radioactivity levels and evaluate the radiological hazards in Usakos marble dome in the Erongo region. **Materials and Methods:** A high purity germanium (HPGe) detector was used in this study to measure the activity concentrations  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$ , and  $^{40}\text{K}$  in marble samples from 20 different points in Usakos marble dome in the Erongo region, Namibia. **Result:** The mean activity concentrations were found in the range of 0.37 to 339.60 Bq kg<sup>-1</sup> for  $^{226}\text{Ra}$ , 0.20 to 210.30 Bq kg<sup>-1</sup> for  $^{232}\text{Th}$ , and 2.96 to 928.70 Bq kg<sup>-1</sup> for  $^{40}\text{K}$ , respectively. The activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$ , and  $^{40}\text{K}$  were used to estimate values of radium equivalent activity (Ra<sub>eq</sub>), Absorbed dose rate (Dr), internal and external hazard indices (H<sub>ex</sub> & H<sub>in</sub>) and the activity utilization index (Iγ). The calculated mean values were Ra<sub>eq</sub> (226.75 Bq kg<sup>-1</sup>), (Dr) (102.99 nGyh<sup>-1</sup>), H<sub>ex</sub>(0.61), H<sub>in</sub> (0.95) and Iγ (1.59). **Conclusion:** From a radiological point, the results of (Dr) and (Iγ) were found above the world recommended average and the performed correlation analysis showed strong positive correlation amongst  $^{232}\text{Th}$  and  $^{226}\text{Ra}$ , which confirms these radionuclides as the main contributors to gamma radiation in the Usakos marble dome. The high activity concentrations at some sampling points higher than the world average value pose possible radiological hazards for the marble samples usage for building materials.

### INTRODUCTION

Humans are continuously being exposed to ionizing radiations that originate from both natural and man-made sources. Natural background radiation makes up about eighty-seven percent of the total doses received by human populations in a year<sup>(1)</sup>. The main contributor to naturally occurring radioactive materials (NORM) are  $^{238}\text{U}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$ <sup>(2, 3)</sup>. Although, the parent element,  $^{238}\text{U}$  does not pose adverse effects on the environment, the inhalation of its daughter nuclide  $^{226}\text{Ra}$  is known to carry a high degree of risk to human organs particularly the lungs resulting to lung cancer<sup>(3)</sup>. Naturally occurring radioactivity in building materials is responsible for the internal and external radiation exposure of human populations living in dwellings made from such building materials<sup>(4-8)</sup>. The distribution of natural radionuclides is not uniform hence, an understanding of their concentrations in human

dwellings is important to quantify human population exposure to NORM, since most humans spend 80-90% of their lifetime indoors<sup>(9-11)</sup>.

Earlier studies have shown that the worldwide average indoor effective dose due to gamma rays originating from building materials is estimated to be about 0.4mSv y<sup>-1</sup><sup>(12-13)</sup>. The presence of natural radionuclides in building materials in an amount exceeding the internationally acceptable limit has received global attention<sup>(13, 14-17)</sup>. The activity of radionuclides depends on geological and geographical setting as well as the geochemical characteristics of the materials<sup>(9, 18)</sup>.

Many studies have investigated the radiological elements in different soil, sediment and rock samples. From a radiological point, the Erongo region in Namibia has attracted the attention of several authors<sup>(19-24)</sup>. However, there exists little or no information on the radiological hazards associated with the marble deposits in the region. The

understanding of the activity concentrations of the marble deposits is needed to properly quantify the radiological hazards from their usage as building materials. The main aim of this study is to ascertain natural radioactivity levels and evaluation of radiological hazards in Usakos marble and to establish a reference line for further and future study on NORM in and around the Usakos, Erongo marble dome.

## MATERIALS AND METHODS

### Study area

Usakos is a mining town in the Erongo region of Namibia (figure 1). It is located at latitude 22° 00' 0.00"S and longitude 15°35'59". Usakos has a population of 3,000 inhabitants and has a catchment area of 58 km<sup>2</sup>. The town of Usakos, as with most towns in the Erongo region, experiences seasonal variation in rainfall. The wet season is from December to April with about 262 mm of rainfall in a year. The rest of the months are generally dry and hot with an average annual temperature of 26°.

### Sampling and sample preparation

Twenty marble samples were collected, once from each of 20 locations 500m apart, at the study area during the year 2018. Initial labeling was done for easy identification. The samples were dried for 120 °C for 24 h, and then crushed using laboratory jaw crusher to 2mm particles, after which 1kg each of the sieved samples was weighed out. All the crushed samples were then carefully homogenized, after which the samples were transferred into a clean empty radon-tight marinielli beaker, marked, and sealed for 31 days to allow the daughter products to attain radioactive secular equilibrium with their parent radionuclides <sup>226</sup>Ra and <sup>232</sup>Th, after which they were counted for 53200 seconds.

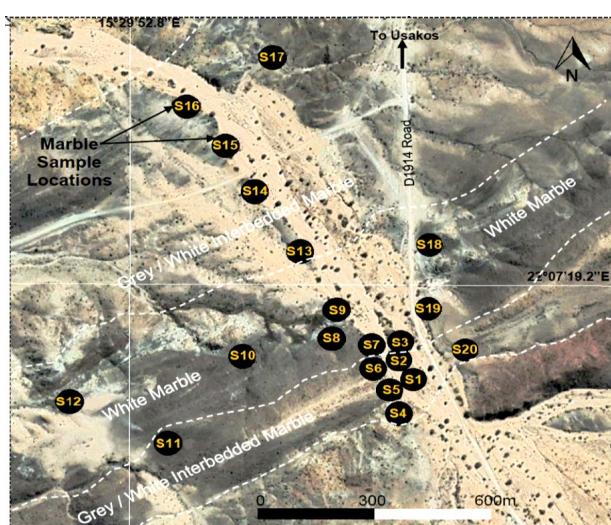


Figure 1. Marble sample collection sites from Usakos marble dome.

### Experimental radiometric analysis

The counting of radionuclides present in marble samples was analyzed with a high-resolution gamma-ray spectrometer using a coaxial (62.80 X 64.80 mm) Canberra high purity germanium (HPGe) detector Model No. GC4520 SN 10882 with 45 % relative efficiency and a resolution of 2.00 keV full width at half maximum (FWHM) at 1.33 MeV peak of <sup>60</sup>Co and 1.200 keV (FWHM) at 122 keV. The detector is shielded with 15 cm lead encasement to reduce the background radiation and cooled using liquid nitrogen. A computer-based Multichannel Analyser (MCA), Genie 2000 software from Canberra, was used for data acquisition and analysis of gamma spectra. Each marble sample was counted for 53200 s in a reproducible sample detector geometry, and the same configuration and geometry was used throughout the analysis. The gamma spectrometry system was energy and efficiency calibrated using a range of gamma-ray energies ranging from 0.060 MeV to 2 MeV mixed radionuclides standard in a 500 ml Marinelli beaker. This energy range was analysed for the absolute photo-peak efficiency and energy calibration of the HPGe detector using a multi-nuclide calibration standard with an initial activity of 40 kBq homogeneously distributed in silicone matrix, which was supplied by Eckert & Ziegler Nuclitec GmbH, Germany, SN. AM5599. The 295.22 keV, 351.93 keV for <sup>214</sup>Pb and 609.32 keV, 1120.29 keV and 1764.49 keV for <sup>214</sup>Bi gamma lines were used in the assessment of activity concentration of <sup>226</sup>Ra, while 911.21 keV for <sup>228</sup>Ac and 968.97 keV and 238.63 keV for <sup>212</sup>Pb were used for <sup>232</sup>Th. The <sup>40</sup>K activity was obtained from the measurement of the single gamma line at 1460.8 keV. The background activity counting due to naturally occurring radionuclides in the room housing the detector was subtracted from obtained peak of each marble samples. Equation 1 was used to calculate the activity concentration A(C) in Bq kg<sup>-1</sup> of the levels of the radioactivity of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K found in each marble samples and the results are presented in table 1.

$$A(C) = \frac{C_{net}}{\epsilon(E) \times I_Y \times t \times m} \quad (1)$$

Where  $C_{net}$  is the counting rate for a specific gamma line given in count per second corrected for background.  $\epsilon(E)$  represent absolute photopeak efficiency,  $I_Y$  is the intensity of gamma-ray line,  $t$  is the time for data collection in seconds and  $m$  is the mass of each sample in kg.

### Radium equivalent activity ( $Ra_{eq}$ )

The concentrations of radionuclides from the activity of <sup>226</sup>Ra, <sup>232</sup>Th and <sup>40</sup>K in marble samples are not uniformly distributed. The uniform distributions in respect of exposure to ionizing radiation can be written in terms of Radium equivalent dose ( $Ra_{eq}$ ). The  $Ra_{eq}$  activity of the measured radionuclides is

used to make comparison of each  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  in the marble samples. The  $\text{Ra}_{\text{eq}}$  activity is measured in the unit of  $\text{Bq kg}^{-1}$ . It was calculated using equation 2.

$$\text{Ra}_{\text{eq}} = \text{AC}_{\text{Ra}} + 1.43\text{AC}_{\text{Th}} + 0.077\text{AC}_{\text{K}} \quad (2)$$

Where  $\text{AC}_{\text{Ra}}$ ,  $\text{AC}_{\text{Th}}$  and  $\text{AC}_{\text{K}}$  are the specific activity concentration of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  respectively. The  $\text{Ra}_{\text{eq}}$  defines the weighted sum of each activity of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  bearing in mind that the radionuclide  $^{226}\text{Ra}$  and the index  $\text{Ra}_{\text{eq}}$  is  $10 \text{ Bq kg}^{-1}$ . For  $^{232}\text{Th}$ ,  $\text{Ra}_{\text{eq}}$  is attributed with  $7 \text{ Bq kg}^{-1}$  while for  $^{40}\text{K}$ ,  $\text{Ra}_{\text{eq}}$  it is  $10 \text{ Bq kg}^{-1}$ .

#### Absorbed dose rate $D_r(\text{nGy/h})$

In this present study, the absorbed dose rates in air at 1m above ground was estimated using the formula in equation 3.

$$D_r(\text{nGy/h}) = 0.427\text{A}_{\text{Ra}} + 0.662\text{A}_{\text{Th}} + 0.043\text{A}_{\text{K}} \quad (3)$$

Where

$\text{A}_{\text{Ra}}$ = specific activity concentration of  $^{226}\text{Ra}$

$\text{A}_{\text{Th}}$ = specific activity concentration of  $^{232}\text{Th}$

$\text{A}_{\text{K}}$ = specific activity concentration of  $^{40}\text{K}$

#### Radiological hazards

The contribution to gamma dose is from different radionuclides. It is therefore important to present radiological hazards as a single quantity. This quantity is known as hazard index, and is calculated according to the model proposed by Krieger (25). The external and internal hazard indices are computed using equation 4 and 5 (12, 25-27).

$$H_{\text{ext}} = \frac{\text{A}_{\text{Ra}}}{370} + \frac{\text{A}_{\text{Th}}}{259} + \frac{\text{A}_{\text{K}}}{4810} \quad (4)$$

$$H_{\text{int}} = \frac{\text{A}_{\text{Ra}}}{185} + \frac{\text{A}_{\text{Th}}}{259} + \frac{\text{A}_{\text{K}}}{4810} \quad (5)$$

To keep gamma radiation dose minimal from building material,  $H_{\text{ext}} \leq 1$  (28-30).

#### Activity utilization index $I_y$

To measure the level of  $\gamma$ -radiation hazard from marble samples, another radiation level index called the activity utilization index is evaluated. The  $I_y$ , was suggested by OECD (16) and was evaluated using equation 6:

$$I_y = \frac{\text{A}_{\text{Ra}}}{150} + \frac{\text{A}_{\text{Th}}}{100} + \frac{\text{A}_{\text{K}}}{1500} \quad (6)$$

For the safe use of the marble stone, evaluated values should be less than unity.

#### Statistical analysis

MS - Excel 2013 software was used for statistical analysis and the statistical test of analysis

of variance (ANOVA) and correlation analysis that were employed to test for statistical significance and correlation that exist amongst the identified radionuclides.

## MATERIALS AND METHODS


The results in table 1 summarize the activity concentration that ranges from  $0.37$  to  $339.60 \text{ Bq kg}^{-1}$  for  $^{226}\text{Ra}$ ,  $0.20$  to  $210.30 \text{ Bq kg}^{-1}$  for  $^{232}\text{Th}$  and  $2.96$  to  $928.70 \text{ Bq kg}^{-1}$  for  $^{40}\text{K}$  respectively. The activity concentrations were calculated from equation 1. The mean and standard deviation of the activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  of all 20 marble samples collected from the Usakos marble dome were found to be  $117.39 \pm 35.30 \text{ Bq kg}^{-1}$ ,  $60.05 \pm 21.05 \text{ Bq kg}^{-1}$  and  $304.95 \pm 88.67 \text{ Bq kg}^{-1}$  respectively. Equation 2 was used to determine  $\text{Ra}_{\text{eq}}$  which is based on the estimation that  $370 \text{ Bq kg}^{-1}$  of  $^{226}\text{Ra}$ ,  $259 \text{ Bq kg}^{-1}$  of  $^{232}\text{Th}$  and  $4810 \text{ Bq kg}^{-1}$  of  $^{40}\text{K}$  each produce an identical gamma ray dose rate and their specific activities are presented in table 1 of column 6. The obtained values shows the minimum radium activity for Us-06 (grey) ( $0.88 \text{ Bq kg}^{-1}$ ) and maximum associated with Us-15 (Black) ( $688.54$ ) with a mean value of  $226.75 \text{ Bq kg}^{-1}$ . The absorbed dose rate ( $D_r$ ) in air due to gamma radiation was calculated using equation 3 and the results were presented in table 2. The calculated  $D_r$  in unit of (nGy/h) due to the activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  were found in the range of  $0.42$  to  $311.15 \text{ nGy/h}$  with a mean value of  $102.99$ . The average value of  $D_r$  is found to be higher than the world recommended value of  $55 \text{ nGy/h}$  (12), implying that the measured absorbed dose rate due to the activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  in air from the studied sites is  $1.9$  times the world allowed value. For building materials used for dwelling purposes to be acceptable, it is recommended that the external and internal hazard indices ( $H_{\text{ext}}$ ), ( $H_{\text{in}}$ ) should have values less than unity (12, 31-33). The  $H_{\text{ext}}$  and  $H_{\text{in}}$  were calculated using equation 4 and 5 and the obtained values presented in table 2 shows the external and internal hazards indices ranging between  $0.00$  to  $1.86$  for  $H_{\text{ext}}$  and  $0.00$  to  $2.78$  for  $H_{\text{in}}$ . The values of samples with codes Us-08, Us-09, Us-10, Us-15 and Us-19 were higher than the recommended value of unity for both  $H_{\text{ext}}$  and  $H_{\text{in}}$  respectively. However, sample Us-03 was higher than the value of unity for  $H_{\text{in}}$  but lower for  $H_{\text{ext}}$  while Us-07 was lower for  $H_{\text{ext}}$  and higher for  $H_{\text{in}}$ . The activity utilization index ( $I_y$ ) was calculated using equation 6 and the results presented in column 6 of table 2. The  $I_y$  results have a minimum value of  $0.00$ , maximum value of  $4.78$  and, mean value of  $1.59$ . Clearly, the mean value of  $I_y$  was found to be higher than the recommended world average value of  $<1$  (12). The tested values of the correlation between the specific activities of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$ , and  $^{40}\text{K}$  as shown in

Figure 3, 4 and 5, showed weak positive correlations with coefficient ( $R^2 = 0.1882$ ) for  $^{40}\text{K}$  and  $^{226}\text{Ra}$ , ( $R^2 = 0.1123$ ) for  $^{40}\text{K}$  and  $^{232}\text{Th}$ , and a strong positive


**Table 1.** Activity concentrations of Radium-226 ( $^{226}\text{Ra}$ ), Thorium-232 ( $^{232}\text{Th}$ ), Potassium-40 ( $^{40}\text{K}$ ) and radium equivalent activity (Raeq) in the marble samples from Usakos.

		Activity Concentration (Bq/kg)			
Codes	Colour	$^{226}\text{Ra}$	$^{232}\text{Th}$	$^{40}\text{K}$	Raeq activity (Bq/kg)
Us-01	Grey	19.30	3.91	63.94	29.81
Us-02	Grey	45.04	37.72	11.53	99.87
Us-03	Grey	180.35	13.99	409.60	231.89
Us-04	Grey	17.06	8.02	128.4	38.42
Us-05	White	6.28	1.15	10.93	8.77
Us-06	grey	0.37	0.20	2.96	0.88
Us-07	grey	149.70	120.76	293.90	345.02
Us-08	grey	253.50	92.72	162.20	398.58
Us-09	White + grey	232.90	149.21	276.30	467.55
Us-10	Beige	179.35	201.53	430.50	500.69
Us-11	White + grey	75.11	26.73	366.70	141.57
Us-12	Beige	57.69	19.27	928.70	156.76
Us-13	Beige	80.14	23.86	200.00	129.66
Us-14	Beige	57.29	17.30	67.58	87.23
Us-15	Black	339.60	210.30	626.10	688.54
Us-16	Grey	71.68	28.27	540.10	153.69
Us-17	White +grey	63.55	20.78	307.80	116.97
Us-18	Grey	134.30	23.93	578.60	213.07
Us-19	Grey	322.90	186.23	485.90	626.62
Us-20	Grey	61.73	15.16	207.20	99.36
Minimum		0.37	0.20	2.96	0.88
Maximum		339.60	210.30	928.70	688.54
Mean $\pm$ SE		117.39 $\pm$ 3 5.30	60.05 $\pm$ 2 21.05	304.95 $\pm$ 88.67	226.75 $\pm$ 15.94
World's average (12)		32	30	420	370

Where, Standard Error (SE) = is the standard deviation, N is the number of observation, Us = Usakos.

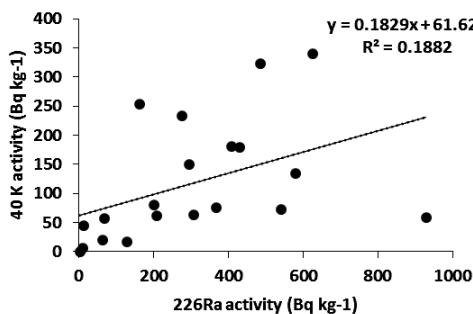

**Figure 3.** The correlation between  $^{40}\text{K}$  and  $^{226}\text{Ra}$  activity.

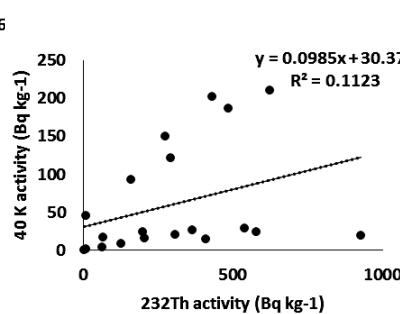


**Figure 4.** The correlation between  $^{40}\text{K}$  and  $^{232}\text{Th}$  activity.

correlation with coefficient ( $R^2 = 0.7312$ ) for  $^{232}\text{Th}$  and  $^{226}\text{Ra}$  respectively.

**Table 2.** Radiological parameters of Absorbed dose rate (Dr), External hazard index (Hex), Internal hazard index (H<sub>in</sub>) and Activity utilization index (AUI) in the marble samples from Usakos.

Codes	Colour	Absorbed dose rate Dr (nGy/H)	External hazard index (H <sub>ex</sub> )	Internal hazard index (H <sub>in</sub> )	Activity utilization index (AUI)
Us-01	Grey	13.58	0.08	0.13	0.21
Us-02	Grey	44.70	0.27	0.39	0.69
Us-03	Grey	103.88	0.63	1.11	1.62
Us-04	Grey	18.12	0.10	0.15	0.28
Us-05	White	3.91	0.02	0.40	0.06
Us-06	grey	0.42	0.00	0.00	0.00
Us-07	grey	156.50	0.93	1.34	2.40
Us-08	grey	176.60	1.08	1.76	2.73
Us-09	White + grey	210.11	1.26	1.89	3.23
Us-10	Beige	228.51	1.35	1.84	3.50
Us-11	White + grey	65.54	0.38	0.59	1.01
Us-12	Beige	77.32	0.42	0.58	1.20
Us-13	Beige	58.62	0.35	0.57	0.91
Us-14	Beige	38.82	0.24	0.39	0.60
Us-15	Black	311.15	1.86	2.78	4.78
Us-16	Grey	72.55	0.42	0.61	1.12
Us-17	White +grey	54.13	0.32	0.49	0.84
Us-18	Grey	98.07	0.58	0.94	1.52
Us-19	Grey	282.06	1.69	2.57	4.33
Us-20	Grey	45.30	0.27	0.44	0.70
Minimum		0.42	0.00	0.00	0.00
Maximum		311.15	1.86	2.78	4.78
Mean $\pm$ SE		102.99 $\pm$ 31 0.61 $\pm$ 0.10	0.95 $\pm$ 0.11	1.59 $\pm$ 0.35	
World's average (12)		55	$\leq 1$	$\leq 1$	$< 1$

Where, Standard Error (SE) = is the standard deviation, N is the number of observation and Us = Usakos.

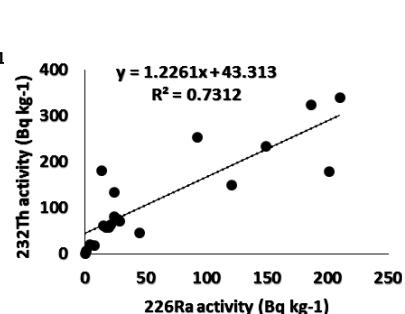

**Figure 5.** The correlation between  $^{232}\text{Th}$  and  $^{226}\text{Ra}$  activity.

## DISCUSSION

The United Nations Scientific Committee on the Effects of Atomic Radiation (UNSCEAR-2000) proposed the acceptable values of activity concentrations of  $^{226}\text{Ra}$  ( $32 \text{ Bq kg}^{-1}$ ),  $^{232}\text{Th}$  ( $30 \text{ Bq kg}^{-1}$ ) and  $^{40}\text{K}$  ( $420 \text{ Bq kg}^{-1}$ ) (12). A comparison of the mean activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  were made with the world average recommended values as well as some studies carried out in other parts of the globe and the results are given in table 3.

It is clearly seen from Table 3 that the average values of  $^{226}\text{Ra}$  and  $^{232}\text{Th}$  in the collected marble samples were higher than the world's average values by a factor of 3.7 for  $^{226}\text{Ra}$ , and 2.0 for  $^{232}\text{Th}$ . The findings also showed that the activity concentrations of  $^{226}\text{Ra}$  and  $^{232}\text{Th}$  in this present study were higher than other published data in Algeria, Cameroon and Saudi Arabia (34-36) as well as some other studies conducted in other countries of the world such as Egypt, Kuwait, Nigeria, China, India and Brazil (37-42). The high concentrations of the radionuclides of  $^{226}\text{Ra}$  and  $^{232}\text{Th}$  measured in this study may be attributed to the geography and geological contents of the Erongo region of Namibia that is characterized by high background radiation (19-24). This is worrisome because high levels of activity concentrations in the marble samples may render the mineral rock radiologically unfit and hazardous for use in building and construction purposes.

However, the mean activity concentration for  $^{40}\text{K}$  is lower than the world allowed value of  $420 \text{ Bq kg}^{-1}$  by a factor of 0.73 (12) but higher than the reported values for the listed countries of Egypt, Kuwait, Nigeria, China, India and Brazil presented in table 3.

**Table 3.** Comparative average values for  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  of present work with world average and other countries.

Country	$^{226}\text{Ra}$	$^{232}\text{Th}$	$^{40}\text{K}$	Ref
<b>Namibia, Usakos</b>	$117.39 \pm 35.30$	$60.05 \pm 21.05$	$304.95 \pm 88.67$	<b>Present study</b>
<b>UNSCEAR-2000</b>	32	30	420	(12)
<b>Egypt</b>	$56.78 \pm 2.5$	$5.95 \pm 1.2$	$1.42 \pm 1.7$	(37)
<b>Kuwait</b>	$3.9 \pm 0.5$	$0.22 \pm 0.08$	$3.7 \pm 0.5$	(38)
<b>Nigeria</b>	2	1	7	(39)
<b>China</b>	8-157	6-166	44-1353	(40)
<b>India, Gujarat</b>	$12 \pm 3$	$3 \pm 2$	$10 \pm 3$	(41)
<b>Brazil, Espírito Santo</b>	$3.0 \pm 0.3$	$2.2 \pm 0.6$	$18.0 \pm 0.1$	(42)

Ra = radium, Th = thorium and K = potassium

The Radium equivalent activity ( $\text{Ra}_{\text{eq}}$ ) is a radiological parameter that is used to relate the external and internal doses due to radon and its progenies (43-45). The  $\text{Ra}_{\text{eq}}$  values from the marble dome site at Usakos, Erongo region were found to be lower than world recommended value  $370 \text{ Bq kg}^{-1}$  (12), while exceeded the allowed values for sample sites with codes Us-08, Us-09 and Us-10 as well as some other sampling sites with codes Us-15 and Us-19. This indicates that the marble samples of

these five locations may have radiological implications if used for building purposes.

The mean absorbed dose rate was calculated and found to be higher than the world average value  $55 \text{ nGy h}^{-1}$  by a factor of 1.87 (12). The average value in this study was also found to be higher than some countries of the world (34, 36) as well as other findings reported in literatures for countries like Nigeria and Cameroon (3, 35).

The radiological indices of internal hazards ( $H_{\text{in}}$ ) and external hazards ( $H_{\text{ex}}$ ) are important indices for the control of exposure originating from radon and its progenies that are carcinogenic in nature since the present health risk to the respiratory organs  $H_{\text{in}} > 1$  was observed in marble samples Us-03, Us-07, Us-08, Us-09, Us-10, Us-15 and Us-19. Also, for  $H_{\text{ex}} > 1$  was estimated for samples with codes Us-08, Us-09, Us-10, Us-15 and Us-19. Although the obtained mean value for  $H_{\text{in}}$  and  $H_{\text{ex}}$  were less than unity which is the recommended value (25), the high values recorded at these sites carries a high radiological risk from the use of the samples for construction and building purposes.

The activity utilization index ( $AUI > 1$ ) was observed in samples Us-03, Us-07, Us-08, Us-9, Us-10, Us-11, Us-12, Us-15, Us-16, Us-18 and Us-19, with a mean value greater than 1 being recommended worldwide (12, 46).

The analysis of variance of the mean activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$ , and  $^{40}\text{K}$  ( $n=20$ ) at  $p < 0.05$  are statistically significant ( $p=0.0000221$ ) (Table 4). This suggests different lithogenic sources of inputs of the radionuclides recorded in the marble samples. According to M. Ngachina et al., natural radionuclides are present in all rocks including marble in varying amounts depending on their concentration levels in the parent rock materials (35).

The strong positive correlation amongst the radioactive nuclides and the associated variables at  $p < 0.05$  suggest that the marble samples from the Usakos marble dome are endowed with thorium and radium, and these elements significantly contribute to the gamma dose from the marble sampling sites. Also, the correlation analysis indicates that both thorium and radium originate from the same decay chain (44, 47).

**Table 4.** Statistical significant test.

Groups	Count	Sum	Average	Variance	
Column $^{226}\text{Ra}$	20	2347.84	117.392	10632.2	
Column $^{232}\text{Th}$	20	1201.04	60.052	5185.693	
Column $^{40}\text{K}$	20	6098.94	304.947	59836.37	
ANOVA					
Source of Variation	SS	df	MS	F	P-value
Between Groups	656255.4	2	328127.7	13.0116	2.21E-05
Within Groups	1437431	57	25218.09		
Total	2093687	59			

Between groups, ANOVA: single factor of paired means ( $n = 20$ ) are statistically significant ( $p < 0.05$ ).

## CONCLUSION

From this study, the mean and range of the activity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$ , and  $^{40}\text{K}$  were 117.39 (0.37-339.60), 304.95 (2.96-928.70) and 226.75 (0.88-688.54)  $\text{Bq kg}^{-1}$  respectively. The mean values of  $\text{Ra}_{\text{eq}}$  activity was found to be less than the acceptable value of 370  $\text{Bq kg}^{-1}$ . The mean value of absorbed dose rate is 102.99  $\text{nGy/h}$ , which is higher than the world recommended value of 55  $\text{nGy/h}$ . The mean values of external and internal hazards indices were below unity however, the mean value of activity utilization index was found to be higher than unity.

## ACKNOWLEDGMENT

We acknowledge the Namibia University of Science and Technology for the financial support provided to carry out this study. We are also thankful to the Risk based Solution Limited, Windhoek, for assistance in transportation and logistics. Finally, we thank the Department of Natural and Applied Sciences, Namibia University of Science and Technology, for giving us access to the High Purity Germanium Detector used for the spectrometric analysis.

**Conflicts of interest:** Declared none.

**Ethics approval and consent to participate:** Not applicable.

**Funding:** Self-funded

**Authors' contributions:** All authors contributed equally to the design of the study, data collection and analysis, and the writing of the manuscript. All authors read and approved the final manuscript.

## REFERENCES

- Khan IU, Qin Z, Xie T, Bin Z, Li H, Sun W, Lewis E (2020) Evaluation of health hazards from radionuclides in soil and rocks of North Waziristan, Pakistan. *Int J of Radiat Res*, **18**(2): 243-253.
- Kant K, Upadhyay SB, Sonkawade RG, Chakarvarti SK (2006) Radiological risk assessment of use of phosphate fertilizers in soil. *Iranian J of Radiat Res*, **4**(2): 63-70.
- Maxwell O, Adewoyin OO, Joel ES, Ehi-Eromosele CO, Akinwumi SA, Usikalu MR, Emeike CP, Embong Z, Hassaina M (2018) Radiation exposure to dwellers due to naturally occurring radionuclides found in selected commercial building materials sold in Nigeria. *J Radiat Res Appl Sc*, **11**: 225-231.
- Ali S, Tufail M, Jamil K, Ahmad A, Klian HA (1996) Gamma-ray activity and dose rate of brick samples from some areas of North West Frontier Province (NWFP), Pakistan. *Sci Total Environ*, **187**(3): 247-252.
- Faheen M, Mujahid SA, Matiullah (2008) Assessment of radiological hazards due to the natural radioactivity in soil and building material samples collected from six districts of Punjab Province-Pakistan. *Radiat Meas*, **43**: 1443-1447.
- Ghose D, Deb A, Bera S, Sengupta R, Patra KK (2008) Assessment of alpha activity of building materials commonly used in West Bengal, India. *J Environ Radiat*, **99**(2): 316-321.
- Turhan S, Baykan UN, Sen K (2008) Measurement of natural radioactivity in building materials used in Ankara and assessment of external doses. *J Radiat Prot*, **28**(1): 83-91.
- Damla N, Cevik U, Kobya AI, Celik N, Yildirim I (2011) Assessment of natural radioactivity and mass attenuation coefficients of brick and roofing tile used in Turkey. *Radiat Meas*, **46**: 701-708.
- Joel ES, Maxwell O, Adewoyin OO, Ehi-Eromosele CO, Embong Z, Saeed MA (2018) Assessment of natural radionuclides and its radiological hazards from tiles made in Nigeria. *Radiat Phys and Chem*, **144**: 43-47.
- Lu X (2005) Natural radioactivity in some building materials of Xi'an, China. *Radiat Meas*, **40**: 94-97.
- Lu X, Zhang X (2008) Radionuclide content and associated radiation hazards of building materials and by-products in Baoji, China. *Radiat Dosim*, **128**: 471-476.
- UNSCEAR (2000) Sources and effects of ionizing radiation, Vol. 1. United Nations Scientific Committee on the Effects of Atomic Radiation. Report of the General Assembly with Scientific Annexes. United Nation, New York.
- Omeye M, Adewoyin OO, Joel ES, Ehi-Eromosele CO, Emenike CP, Usikalu MR, Akinwumi SA (2018) Natural radioactivity concentrations of  $^{226}\text{Ra}$ ,  $^{232}\text{Th}$  and  $^{40}\text{K}$  in commercial building materials and their lifetime cancer risk assessment in dwellers. *Human and Ecological Risk Assessment*, **24**(8): 2036-2053.
- Rahman SU, Rafique M, Jabbar AM (2013) Radiological hazards due to naturally occurring radionuclides in the selected building materials used for the construction of dwellings in four districts of the Punjab province, Pakistan. *Radiat Prot Dosim*, **153**(3): 352-360.
- Righi S and Bruzzi L (2006) Natural radioactivity and radon exhalation in building materials used in Italian dwellings. *J Environ Radioact*, **88**: 158-170.
- OECD (Organization for Economic Co-operation and Development), 1979. Exposure to radiation from radioactivity in building materials. Report by a Group of Experts of the OECD Nuclear Energy Agency.
- Lee SC, Kim CK, Lee DM, Kang HD (2001) Natural radionuclides contents and radon exhalation rates in building materials used in South Korea. *Radiat Prot Dosim*, **94**(3): 269-274.
- Hesham AY, Hamed IM, Korany KA (2019) Assessment of radiological hazards indices in Abu Rusheid area, southeastern desert, Egypt, using gamma ray spectroscopy. *Arab J of Nuc Sci and Appl*, **52**(2): 132-141.
- Onjefu SA, Kgabi NA, Taole SH, Grant C, Antoine J (2017) Assessment of natural radionuclide distribution in shore sediment samples collected from the north dune beach, Henties Bay, Namibia: *J of Radiat Res and Appl Sci*, **10**: 301-306.
- Oyedele JA (2006) Assessment of natural radioactivity in soils of Windhoek City, Namibia, Southern Africa. *Radiat Prot Dosim*, **3**: 337-340.
- Zivuku M, Kgabi NA, Tshivhase MV (2016) Elementary concentration of natural occurring radioactive materials in soils nearby uranium sites of Erongo region, Namibia. *Euro j of Sci Res*, **4**: 402-410.
- Zivuku M, Kgabi NA, Tshivhase MV (2018) Excess lifetime cancer risk due to natural radioactivity in soils: Case of Karibib town in Namibia. *The African Review of Physics*, **13**: 0012.
- Steinhausler, F., Lettner, H. (1992) Radiometric Survey in Namibia. *Radiat Dosim*, **1**(4): 553-555.
- Oyedele JA, Shimboyo S, Sitoko S, Gaoeseb F (2010) Assessment of natural radioactivity in soils of rossing uranium mine and its satellite town in western Namibia, Southern Africa. *Nucl Instr Met in Phys Res A*, **619**: 467-469.
- Krieger (1981) Radioactivity of construction materials, Betonwerk Fertigteil Techn, **47**: 468.
- Farai IP and Ademola JA (2005) Radium equivalent activity concentrations in concrete building blocks in eight cities in Southwestern Nigeria. *Journal of Environmental Radioactivity*, **79**(2): 119-125.
- Hamid BN, Alam MN, Chowdhury MI, Islam MN (2002) Study of natural radionuclides concentrations in an area of elevated radiation background in the Northern districts of Bangladesh. *Radiation Protection Dosimetry*, **98**(2): 227-230.
- Reda E, Mohammed AAO, El-Montaser MS, Atef E (2018) Natural Radioactivity levels and radiological hazards in soil samples around Abu Karqas Sugar Factory. *J Environ Sci Technol*, **11**: 28-38.
- Harikrishnan N, Ravisankar R, Chandrasekaran A, Gandhi MS, Vijayagopal P (2018) Assessment of gamma radiation and associated radiation hazards in coastal sediments of south east coast of Tamilnadu, India with statistical approach. *Ecotoxicology and Environmental Safety*, **162**: 521-528.
- Prakash MM, Kaliprasad CS, Narayana Y (2017) Study on natural radioactivity in rocks of Coorg district, Karnataka state, India. *J Radiat Res Appl Sci*, **10**: 128-134.
- Zaid Z, AL-Fatlawi YFK (2019) Evaluation of natural radioactivity in

granite and marble used as flooring materials in Baghdad Province, Iraq. *Iraqi J Sci*, **59**(3A): 1183-1188.

32. UNSCEAR (1993) United Nations Scientific Committee on the Effects of Atomic Radiation. Exposure from natural sources of radiation. UNSCEAR, New York.

33. Ridha AA (2013) Determination of radionuclides concentrations in construction materials used in Iraq. Ph.D. Thesis, College of Science, Al-Mustansiriyah University.

34. Amrani D and Tahtat M (2001) Natural radioactivity in Algerian building materials. *Applied Radiation and Isotopes*, **54**: 687-689.

35. Ngachina M, Garavaglia M, Giovanic C, Kwato NMG, Nourredined A (2007) Assessment of natural radioactivity and associated radiation hazards in some Cameroonian building materials. *Radiat Meas*, **42**: 61-67.

36. Al-Saleh FS and Al-Berzan B (2007) Measurements of natural radioactivity in some kinds of marble and granite used in Riyadh Region. *J. Nucl Radiat Phys*, **2**: 25-36.

37. Fares S, Yassene, AAM, Ashour, A, Abu-Assy, MK, Abd El-Rahman, M (2011) Natural radioactivity and the resulting radiation doses in some kinds of commercially marble collected from different quarries and factories in Egypt, *Natural Science*, **3**(10): 895-905.

38. Bou-rabee F, Bem H (1996) Natural radioactivity in building materials utilized in the state of Kuwait. *J Radioanal Nucl Chem*, **213** (2): 143-149.

39. Ademola AK, Hammed OS, Adejumobi CA (2008) Radioactivity and dose assessment of marble samples from Igbedi Mines, Nigeria. *Radiat Prot Dosim*, **132**(1): 94-97.

40. LU X (2007) Radiometric analysis and radiological hazards of Chinese commercial marble. *Radiat Eff Defects Solids*, **162**(6): 455-462.

41. Sahoo BK, Nathwani D, Eappen KP, Ramachandran TV, Gaware JJ, Mayya YS (2007) Estimation of radon emanation factor in Indian building materials. *Radiat Meas*, **42**: 1422 – 1425.

42. Reginaldo R, Aquino RR, Pecequilo BRS (2011) Natural radioactivity analysis in commercial marble samples of southeast region in espírito santo state: preliminary results. International Nuclear Atlantic Conference - INAC 2011 Belo Horizonte, MG, Brazil, October 24-28, 2011 ASSOCIAÇÃO BRASILEIRA DE ENERGIA NUCLEAR – ABEN.

43. Beretka J and Mathew PJ (1985) Natural radioactivity of Australian building materials, industrial wastes and by-products. *Health Phys*, **48**: 87-95.

44. Imani M, Adelikhah M, Shahrokhi A, Azimpour G, Yadollahi A, Kocsis E, Toth-Bodrogi E, Kovacs T (2021) Natural radioactivity and radiological risks of common building materials used in Semnan Province dwellings, Iran. *Environ Sci Pollut Res*, **28**(30): 41492-41503.

45. Khatun MA, Ferdous J, Haque MM (2018) Natural radioactivity measurement and assessment of radiological hazards in some building materials used in Bangladesh. *J Environ Prot*, **9**: 1034-1048.

46. Fares S, Yassene AAM, Ashour A, Abu-Assy AMK, Abd El-Rahman M (2011) Natural radioactivity and the resulting radiation doses in some kinds of commercially marble collected from different quarries and factories in Egypt. *Natural Sci*, **3**(10): 895-905.

47. Uwatse OB, Olatunji MA, Khandaker MU, Amin YM, Bradley DA, Alkhorayef M, Alzimami K (2015) Measurement of natural and artificial radioactivity in infant powdered milk and estimation of the corresponding annual effective dose. *Environment Engineering Science*, **32**(10): 1-10.

